

High performance Volume Phase Holographic Grism and its Applications to Near-infrared Astronomy

Kaoru Nakajima^a, Noboru Ebizuka^b, Masanori Iye^c, and Kashiko Kodate^d

^a Graduate School of Science, Japan Women's University, ^b Department of Astrophysics, Nagoya University, ^c National Astronomical Observatory of Japan J.W.U.

Background

VPH (Volume Phase Holographic) grating

Principle

VPH grism = VPH grating + 2 prisms

Bragg's condition

$$2n_g \Lambda \sin \theta_B = m\lambda$$

Λ : grating pitch
 n_g : refractive index
 λ : incident light
 θ_B : bragg angle
 θ_{in} : angle of incidence
 θ_{out} : diffraction angle
 m : diffraction order

Features

Direct vision transmission type

Diffacted light passes straight-through transmission at a specific wavelength

High efficiency

The diffraction efficiency of VPH gratings can approach nearly 100%, when the angle of incident light satisfies Bragg's condition.

High dispersion

The VPH grating has the potential for achieving high dispersion in wide area by using holographic exposure.

Photosensitive media

The photopolymer is transparent, low scattering and small absorption even in K-band.

Challenges

High efficiency and wide range of spectral bandwidth in the near infrared region are needed.

Maximum diffraction efficiency

$$= \sin^2 \frac{t \cdot \Delta n}{\lambda \cos \theta_B}$$

Δn : refractive index modulation,
 t : thickness of a VPH grating,
 λ : incident wavelength,
 θ_B : bragg angle

$$\lambda \propto t \quad \begin{matrix} \lambda \rightarrow \text{longer} \\ t \rightarrow \text{larger} \end{matrix} \quad \lambda_{FWHM} \propto \frac{1}{t}$$

When the thickness of a VPH grating is larger,

Low refractive index modulation
 Shrinkage of resin
 Narrow spectral bandwidth

Design and fabrication of K-band VPH gratings

Algorithm of VPH grating

Design

Longer the center wavelength, larger the value of $(t\Delta n)$ has to be increased.
 $\lambda_{FWHM} \propto (1/t) \cdot t \cdot (1/\Delta n) \rightarrow \text{high } \Delta n$

Calculation of optimal thickness and refractive index modulation using Rigorous Coupled-Wave Analysis (RCWA)

Fabrication


Fabrication of uniform substrate for VPH grating
 Interference patterns were recorded on the substrate by two beam exposure
 Consolidation process of ultra violet exposure

Evaluation

high efficiency, broad spectral bandwidth and small wave front error

VPH gratings

Dependence of spectral bandwidth and refractive index modulation on the thickness of gratings

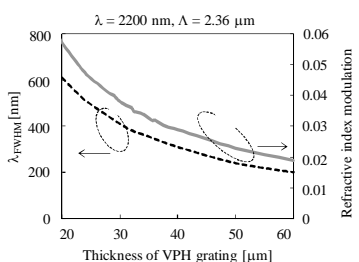


Wide spectral bandwidth
 High efficiency


High refractive index modulation is needed.

To block the phase fluctuation is very important.

Fabrication process of VPH grating

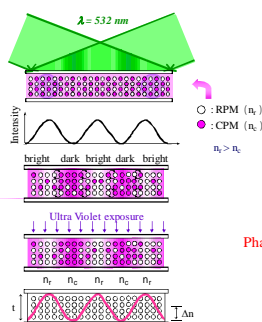

Optical setup for fabrication of VPH grating with active phase control

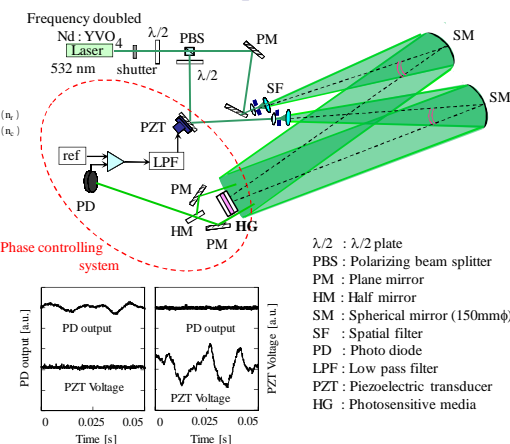


Ref1) K. Oka, A. Yamada, Y. Komai, E. Watanabe, N. Ebizuka, T. Teranishi, M. Kawabata, K. Kodate, Proc. of SPIE 5005, 8-19 (2005).

Ref2) K. Nakajima, Y. Komai, E. Watanabe, F. Moritsuka, S. Anzai, and K. Kodate, Opt. Rev. 14, No.4, 201-207(2007).

Ref3) K. Nakajima, N. Ebizuka, M. Iye, and K. Kodate, Proc. SPIE, Vol.7014, p.70141Q (2008).


Evaluation

Diffraction efficiency dependence on the 2200nm-blaze wavelength

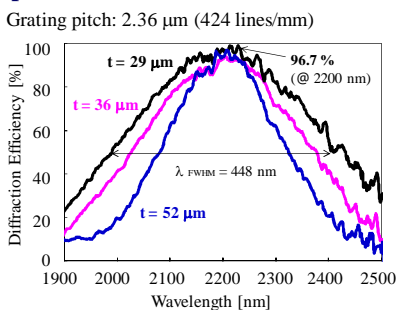


We succeeded the control of the spectral bandwidth and got wide spectral bandwidth with high efficiency.

Diffraction efficiency dependence on wavelength

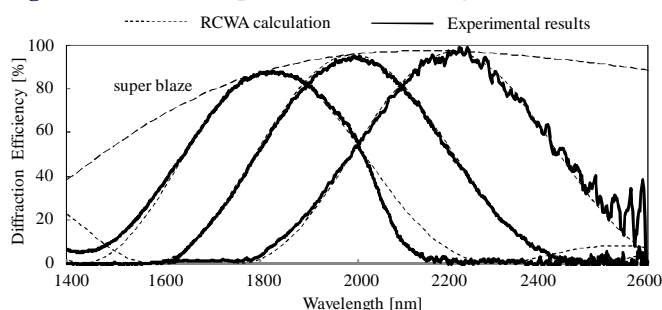

High efficiency: 96.7%, wide spectral bandwidth: 448 nm, small wavefront error: 0.041 lambda at 2200 nm

The 1st order diffraction wavefront error measurement by Zygo interferometer

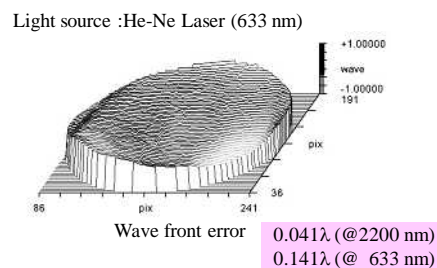

High-performance VPH grating was successfully fabricated !!

Conclusions

- * We showed that high refractive index modulation is needed to get high performance VPH gratings in near infrared region using calculation engine RCWA.
- * We designed VPH gratings by using high-power light source for holographic exposure and active feedback phase control.
- * We succeeded the control of the spectral bandwidth and got wide spectral bandwidth with high efficiency.
- * The diffraction efficiency reached 96.7% ($\lambda=2200$ nm), refractive index modulation is 0.039, spectral bandwidth (λ_{FWHM}) is 448 nm, and small wavefront error is 0.041 waves in r.m.s. at 2200 nm.
- * The VPH grism is one of the promising dispersion devices for astronomical observation in the near-infrared region. The prototype will soon be installed into MOIRCS, and will be tested in observation in partnership with Tohoku University and the National Astronomical Observatory of Japan.

Acknowledgements

We would like to thank Nippon Paint Corp. for providing us with the photosensitive media for fabrication of VPH gratings. We appreciate Dr. Noboru Ebizuka (Nagoya Univ.), Dr. Jun Mizuno (Japan women's Univ.), Prof. Takashi Ichikawa, Prof. Toru Yamada, and Dr. Chihiro Tokoku (Tohoku Univ.) for many helpful suggestions. We utilized facilities at the Advanced Technology Center of NAOJ for grating measurements.